

11 April 2023

PROSPECH IDENTIFIES HIGH-GRADE RARE EARTH OXIDES AND HAFNIUM OVER 4KM STRIKE AT JOKIKANGAS PROJECT, FINLAND

Highlights

- Mineralisation database¹ at recently acquired Jokikangas project and surrounding Otanmaki area returns rare earth element oxide (REO) intercepts in diamond drill hole samples over a strike length of 4 kilometres.
- Results² include:
 - o KA02: 0.20m @24,448 ppm TREO and 4,700 ppm Niobium from 74.2m
 - o KA03: 0.15m @15,346 ppm TREO and 2,980 ppm Niobium from 9.2m
 - KA03: 0.17m @ 8,690 ppm TREO and 2,030 ppm Niobium from 57.3m
 - o JO11: 0.20m @ 2,106 ppm TREO from 54.1m
 - o JO12: 0.20m @ 1,704 ppm TREO from 26.9m
 - o JO12: 0.40m @ 4,509 ppm TREO from 42.2m
 - JO13: 0.50m @ 7,556 ppm TREO and 940 ppm Hafnium from 22.6m
 - JO13: 0.30m @ 10,445 ppm TREO and 1,160 ppm Hafnium from 32.8m
 - KO06: 0.40m @ 2,865 ppm TREO and 510 ppm Hafnium from 85.6m
- Drill core sampling was limited to narrow intervals for academic purposes, resulting in only narrow intersection intervals reported.
- Prospech has commenced sampling wider intervals of the Jokikangas drill core.
- Drill core is available from 36 diamond drill holes at Jokikangas and 68 diamond drill holes at Korsnas.
- Prospech has applied to expand the Jokikangas project to cover open ground with reported vanadium mineralisation.

¹ Age and Origin of the Nb Zr Ree Mineralisation in the Paleoproterozioc granitoids at Otanmaki, Central Finland. Bulletin of the Geological Society of Finland. Volume 92, 2020.

² All values reported in Total Rare Earth Oxide (TREO) amounts unless otherwise stated.

Prospech Managing Director Jason Beckton commented: "We are delighted to reveal results from our archive search and compilation of historical drill core at Jokikangas as the new Bambra Oy assets are incorporated into our portfolio.

According to Oulo University and Geological Survey of Finland, the peralkaline alkali feldspar granites are the most probable source for the Rare Earth Element (REE) and High Field Strength Element (HFSE) mineralised felsic dikes and sheet-like intrusions. Magnetic anomalies within the "enriched" alkali feldspar granite block and its surroundings, as well as the contact areas of this block against the monzogranite block, offer interesting potential for REE-HFSE mineralisation.

High Field Strength Elements which include Niobium and Hafnium are characterised by their ability to form strong bonds with other atoms, due to their electronic structure. This property makes them useful in a variety of technological applications where strength, durability and resistance to corrosion are required.

There is a significant increase in demand for locally supplied critical minerals in Europe and the government is strongly committed to fulfilling as much of the demand as possible from local sources.

The brownfield targets of Jokikangas, Korsnas, and Saarenkylä in Finland, which have been explored since 2018, provide us with an exciting opportunity to enter the REE and lithium space in the EU and we are planning to accelerate our exploration on the back of these results."

About Finland and the Finland Projects

Finland is recognised as a favourable mining jurisdiction within the European Union and has been ranked ninth globally in the 2021 Fraser Institute Annual Survey of Mining Companies' Policy Perception Index and 13th in the Investment Attractiveness Index, surpassing jurisdictions such as Queensland, NSW, and Victoria.



Location map of the Bambra projects in Finland


Prospech's geological team has prior experience working in Finland, and the acquisition of Bambra will provide a local permitting and administration team with extensive country experience.

Project summaries

Extensive mapping and sampling of the mineralised horizons was conducted by the Geological Survey of Finland (GTK), and Prospech aims to prioritise the grade and tonnage potential of each occurrence to plan and permit drilling in the near future.

Jokikangas REE Project

Jokikangas REE project encompasses two blocks, Jokikangas and Honkamäki, covering a total area of 28.37km², while the third-party Otanmaki (05) Oy tenure is indicated by the blue area in the map bello. Jokikangas and Honkamäki cover a REE-vanadium mineralised belt of rocks.

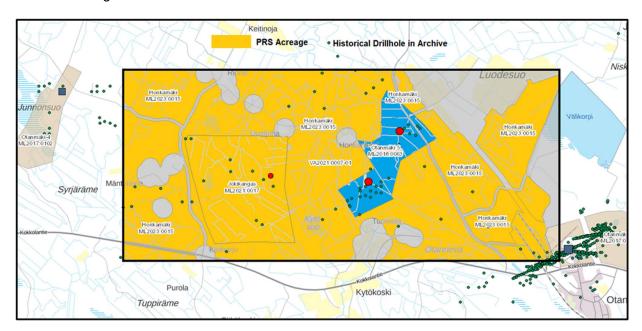

Jokikangas tenements

Elongated bodies containing up to 2.0% TREE are characterised by sericitic alteration and a spatial relationship with pegmatites in a mineral assemblage that includes fergusonite (Nb, Y, REO), allanite (LREE), and columbite-tantalite (Nb).

Prospech holds rights to exploration tenure surrounding the Kontioaho and Katajakangas targets currently held by Otanmaki (O5) Oy, with mineralisation that is continuous but lightly drilled. The mineralisation at Katajakangas features a high-grade zone approximately 12m thick in its central part, surrounded by a lower-grade zone at the margins.

Archived drillhole data indicates an opportunity to extend mineralisation northwest of Otanmaki (05) Oy's Kontioaho operation and west of the Katajakangas operation (both depicted as red dots on the Otanmaki (05) Oy map above) onto the Jokikangas project.

Korsnas REE Project

The Korsnas REE project surrounds a former lead mine at Korsnas, which operated from 1959 to 1972 and produced 0.87Mt of ore with an average of 3.6% Pb. The deposit was found to be prospective for REE due to the presence of allanite and a few other REE minerals.

During pilot production of an REE concentrate in the early 1970s, it was discovered that the ore contained 0.83% TREO. The mineralisation is situated in a fault zone that trends north-south and is filled with a vein consisting of coarse-grained calcite, feldspar, diopside and REE-bearing apatite.

Previous mine operators have reported total REE content of samples ranging from 0.7% to 2.2%, with LREE being the dominant component. The samples also exhibit high europium (Eu) content, with values ranging from 66 to 242 ppm and thorium (Th) content ranging from 107 to 604 ppm.

There is core from 68 government stored drillholes from the immediate vicinity of the Korsnas mine that remain unsampled and there is also a group of unmined carbonate veins or dykes that up to 20m wide that may contain REE grades.

Saarenkylä Lithium-Berrylium Project

The Saarenkylä exploration reservation area is situated in a region with a known occurrence of lithium pegmatite, where lithium-cesium-tantalum (+/- beryllium) has been observed in exposed sequences of pegmatite.

The area is located within the Northern Ladoga belt, which is known for various minerals such as Sn, Zn, Pb, U, Au, W, Fe, and V. A mineral occurrence has been identified in pyroxene skarn with potential associations of nearby mineralisation within the Myerskaja Fault zone.

The mineralisation at this location includes occurrences of beryl, bismuthinite (Bi), scheelite (W), cassiterite (Sn), and native gold, which are conformable. Field mapping and sampling will be required to determine the continuity of the occurrence.

Prospech has filed a new reservation notification with the Finnish Mining Authority to extend the project area over the known lithium pegmatite occurrence area.

For further information, please contact.

Jason Beckton Managing Director Prospech Limited +61 (0)438 888 612

Competent Person's Statement

The information in this Report that relates to Exploration Results is based on information compiled by Mr Jason Beckton, who is a Member of the Australian Institute of Geoscientists. Mr Beckton, who is Managing Director of the Company, has sufficient experience which is relevant to the style of mineralisation and type of deposit under consideration and to the activity which he is undertaking to qualify as a Competent Person as defined in the 2012 edition of the 'Australasian Code for Reporting of Exploration Results, Mineral Resources and Ore Reserves'. Mr Beckton consents to the inclusion in this Report of the matters based on the information in the form and context in which it appears.

This announcement has been authorised for release to the market by the Managing Director

JORC Code, 2012 Edition - Table 1 Schopfer, Hodrusa

Section 1 Sampling Techniques and Data

Criteria	JORC Code explanation	Commentary
Sampling techniques	Nature and quality of sampling (eg cut channels, random chips, or specific specialised industry standard measurement tools appropriate to the minerals under investigation, such as down hole gamma sondes, or handheld XRF instruments, etc). These examples should not be taken as limiting the broad meaning of sampling. Include reference to measures taken to ensure sample representivity and the appropriate calibration of any measurement tools or systems used. Aspects of the determination of mineralisation that are Material to the Public Report. In cases where 'industry standard' work has been done this would be relatively simple (eg 'reverse circulation drilling was used to obtain 1 m samples from which 3 kg was pulverised to produce a 30 g charge for fire assay'). In other cases more explanation may be required, such as where there is coarse gold that has inherent sampling problems. Unusual commodities or mineralisation types (eg submarine nodules) may warrant disclosure of detailed information.	N/A
Drilling techniques	Drill type (eg core, reverse circulation, open-hole hammer, rotary air blast, auger, Bangka, sonic, etc) and details (eg core diameter, triple or standard tube, depth of diamond tails, face-sampling bit or other type, whether core is oriented and if so, by what method, etc).	Assumed Diamond HQ, NQ and BQ drilling.
Drill sample recovery	Method of recording and assessing core and chip sample recoveries and results assessed. Measures taken to maximise sample recovery and ensure representative nature of the samples. Whether a relationship exists between sample recovery and grade and whether sample bias may have occurred due to preferential loss/gain of fine/coarse material.	Historic Core N/A.
Logging	Whether core and chip samples have been geologically and geotechnically logged to a level of detail to support appropriate Mineral Resource estimation, mining studies and metallurgical studies. Whether logging is qualitative or quantitative in nature. Core (or costean, channel, etc) photography. The total length and percentage of the relevant intersections logged.	The complete core is to be relogged.
Sub-sampling techniques and sample preparation	If core, whether cut or sawn and whether quarter, half or all core taken. If non-core, whether riffled, tube sampled, rotary split, etc and whether sampled wet or dry. For all sample types, the nature, quality and appropriateness of the sample preparation technique. Quality control procedures adopted for all subsampling stages to maximise representivity of samples. Measures taken to ensure that the sampling is representative of the in situ material collected, including for instance results for field duplicate/second-half sampling. Whether sample sizes are appropriate to the grain size of the material being sampled.	N/A.
Quality of assay data and laboratory tests	The nature, quality and appropriateness of the assaying and laboratory procedures used and whether the technique is considered partial or total. For geophysical tools, spectrometers, handheld XRF instruments, etc, the parameters used in determining the analysis including instrument make and model, reading times, calibrations factors applied and their derivation, etc. Nature of quality control procedures adopted (eg standards, blanks, duplicates, external laboratory	Samples are stored in the Loppi relogging facility.

Criteria	JORC Code explanation	Commentary
	checks) and whether acceptable levels of accuracy (ie lack of bias) and precision have been established.	
Verification of sampling and assaying	The verification of significant intersections by either independent or alternative company personnel. The use of twinned holes. Documentation of primary data, data entry procedures, data verification, data storage (physical and electronic) protocols. Discuss any adjustment to assay data.	N/A.
Location of data points	Accuracy and quality of surveys used to locate drill holes (collar and down-hole surveys), trenches, mine workings and other locations used in Mineral Resource estimation. Specification of the grid system used. Quality and adequacy of topographic control.	UTM projection Zone 35N.
Data spacing and distribution	Data spacing for reporting of Exploration Results. Whether the data spacing and distribution is sufficient to establish the degree of geological and grade continuity appropriate for the Mineral Resource and Ore Reserve estimation procedure(s) and classifications applied. Whether sample compositing has been applied.	Subsampling below 0.2m was undertaken by previous companies.
Orientation of data in relation to geological structure	Whether the orientation of sampling achieves unbiased sampling of possible structures and the extent to which this is known, considering the deposit type. If the relationship between the drilling orientation and the orientation of key mineralised structures is considered to have introduced a sampling bias, this should be assessed and reported if material.	No bias is believed to be introduced by the sampling method.
Sample security	The measures taken to ensure sample security.	N/A
Audits or reviews	The results of any audits or reviews of sampling techniques and data.	No audits or reviews of the data management system have been carried out.

Section 2 Reporting of Exploration Results

Criteria	JORC Code explanation	Commentary
Mineral tenement and land tenure status	Type, reference name/number, location and ownership including agreements or material issues with third parties such as joint ventures, partnerships, overriding royalties, native title interests, historical sites, wilderness or national park and environmental settings.	Prospech Limited has entered into an earn-in agreement with the shareholders of Bambra Oy ('Bambra'), a company incorporated in Finland, to earn up to a 100% interest in Bambra and therefore, acquire Bambra's 100% interest in the Jokikangas REE project, the Korsnas REE project and Saarenkylä lithium project in Finland ('Finland Projects').
	The security of the tenure held at the time of reporting along with any known impediments to obtaining a license to operate in the area.	Prospech's exclusive right to acquire 100% of Bambra is staged over 2 years with consideration being an initial payment of \$25,000 ('Exclusivity Payment'), a series of exploration and evaluation expenditures and the issuance of Prospech consideration shares.
		For the first year option, Prospech can earn a 51% interest in Bambra by the expenditure of \$100,000, including the Exclusivity Payment, on the exploration and evaluation of the Finland Projects and, if exercised by Prospech, the issue of 3 million fully paid ordinary shares in Prospech to the shareholders of Bambra ('First Option').
		For the second year option, subject to the completion of the First Option, Prospech can earn the remaining interest in Bambra, so as to own 100% of Bambra, by the expenditure of \$200,000 on the exploration and evaluation of the Finland Projects and, if exercised by Prospech, the issue of a further 3 million shares to the shareholders of Bambra.
		The laws of Finland relating to exploration and mining have various requirements. As the exploration advances specific filings and environmental or other studies may be required. There are ongoing requirements under Finnish mining laws that will be required at each stage of advancement. Those filings and studies are maintained and updated as required by Prospech's environmental and permit advisors specifically engaged for such purposes. The Company is the manager of operations in accordance with generally accepted mining industry standards and practices.

Criteria	JORC Code explanation	Commentary											
Exploration done by other parties	Acknowledgment and appraisal of exploration by other parties.	The area of Otanmaki – Jokikangas has been mapped, boulder sampled and drilled by private companies including Rautaruuki Oy and Outokumpu Oy from 1981. In 2020 the project was subject to core resampling by GTk (Finnish Geological Survey) and University of Oulo, utilising ALS Chemex Laboratory in Outokumpu, Finland. Karenlampi et 2020.											
Geology	Deposit type, geological setting and style of mineralisation.	The Otanmäki rare earth element (REE) area is composed of diverse rock types such as granite gneisses, granites, alkali gneisses, quartz-feldspar schists, amphibolites, and mica schists. The formation of REE-bearing minerals in thi area is associated with hydrothermal alteration of the host rocks caused by the intrusion of gabbros and anorthosites the Otanmäki region.											
Drill hole	A summary of all information material to the	Drill Hole Collar Information (All UTM Zone 35N)											
Information	understanding of the exploration results including a	HOLE_ID NORTH UTEAST UTM FINAL_DEPTH RL DATE AZIMUTH DIP											
	tabulation of the following information for all Material drill holes:	JOKIKANGAS-001 7111504 498886.2 148.8 1000 1984 305 -53 JOKIKANGAS-002 7111216 499274.1 126.5 1000 1984 305 -53											
	easting and northing of the drill hole collar	JOKIKANGAS-003 7111345 499088.1 158.3 1000 1984 305 -50 JOKIKANGAS-004 7110591 500214.7 190.3 1000 1984 305 -51											
	elevation or RL (Reduced Level – elevation above	JOKIKANGAS-005 7110792 500457.6 194.2 1000 1984 307 -53											
	sea level in metres) of the drill hole collar	JOKIKANGAS-006 7110572 498958.2 228.6 1000 1984 306 -47 JOKIKANGAS-007 7109980 498388.4 157.7 1000 1984 317 -63											
	dip and azimuth of the hole down hole length and interception depth	JOKIKANGAS-008 7110922 497731.7 151.4 1000 1984 90 -47 JOKIKANGAS-009 7110922 497548.8 57.5 1000 1984 90 -49											
	hole length.	JOKIKANGAS-010 7111181 497143.9 188.7 1000 1984 54 -45 JOKIKANGAS-011 7110821 496424 182 1000 1984 90 -41											
	If the exclusion of this information is justified on the	JOKIKANGAS-012 7110837 496584.2 128 1000 1984 90 -45											
	basis that the information is not Material and this exclusion does not detract from the understanding of	JOKIKANGAS-013 7111215 496655.1 177 1000 1984 90 -45 JOKIKANGAS-014 7110489 499070.2 124 1000 1984 306 -54											
	the report, the Competent Person should clearly	KATAJAKANGAS-001 7111117 503056.5 85.02 1000 1973 23 -3 KATAJAKANGAS-002 7110485 503211.5 203.1 1000 1983 23 -5											
	explain why this is the case.	KATAJAKANGAS-003 7110450 503355.4 156.5 1000 1983 23 -6 KATAJAKANGAS-006 7111551 501127.3 178.9 1000 1984 360 -6											
		KATAJAKANGAS-009 7110597 502462.8 203.1 1000 1984 22 -6											
		KATAJAKANGAS-010 7110462 501652.1 202.6 1000 1984 360 -5 KONTIOAHO-001 7113371 500207.7 137.45 1000 1980 306 -5											
		KONTIOAHO-002 7113371 500207.7 137.45 1000 1980 306 -5 KONTIOAHO-003 7112008 501656.1 210.7 1000 1984 45 -7											
		KONTIOAHO-004 7112216 501865 144.3 1000 1984 45 -(KONTIOAHO-005 7113096 501177.3 159 1000 1984 52 -(
		KONTIOAHO-006 7112741 499572.9 148 1000 1984 297 -5											
		KONTIOAHO-007 7113021 500062.7 184.6 1000 1984 305 -5 KONTIOAHO-012 7112985 501035.3 131.5 1000 1985 52 -5											
		KONTIOAHO-014 7112701 500247.7 233.7 1000 1984 306 -7											
		OTM11007 7116220 3501523 57.85 1000 2011 40 -6 OTM11008 7116930 3500505 101.8 1000 2011 305 -6											
		OTM11009 7116675 3500675 111.05 1000 2011 305 -6											
		OTM11010 7112845 3496550 69.95 1000 2011 290 -4 OTM11011 7114480 3498640 85.55 1000 2011 270 -4 OTM11012 7114704 3498628 113.9 1000 2011 270 -4											
		Assay results, refer below to Appendix 1.											
Data aggregation methods	In reporting Exploration Results, weighting averaging techniques, maximum and/or minimum grade truncations (eg cutting of high grades) and cut-off grades are usually Material and should be stated. Where aggregate intercepts incorporate short lengths of high grade results and longer lengths of low grade results, the procedure used for such aggregation should be stated and some typical examples of such aggregations should be shown in detail. The assumptions used for any reporting of metal equivalent values should be clearly stated.	A minimum sample length is 0.4m generally but can be as low as 0.15m is observed in historical sampling.											
Relationship	These relationships are particularly important in the	Mineralisation is mesothermal contact related between											
between mineralisation widths and intercept lengths	reporting of Exploration Results. If the geometry of the mineralisation with respect to the drill hole angle is known, its nature should be reported. If it is not known and only the down hole lengths are reported, there should be a clear statement to this	intrusives of Paleoproterozoic age.											
Diagrama	effect (eg 'down hole length, true width not known').	The location and recults received for a constant											
Diagrams	Appropriate maps and sections (with scales) and tabulations of intercepts should be included for any significant discovery being reported These should include, but not be limited to a plan view of drill hole collar locations and appropriate sectional views.	The location and results received for some drill-core samplare displayed in the attached maps and/or tables. Coordinates are UTM Zone 35N.											
Balanced reporting	Where comprehensive reporting of all Exploration Results is not practicable, representative reporting of both low and high grades and/or widths should be practiced to avoid misleading reporting of Exploration Results.	Results for all samples collected in the past are displayed the attached maps and/or tables.											

Criteria	JORC Code explanation	Commentary
Other substantive exploration data	Other exploration data, if meaningful and material, should be reported including (but not limited to): geological observations; geophysical survey results; geochemical survey results; bulk samples – size and method of treatment; metallurgical test results; bulk density, groundwater, geotechnical and rock characteristics; potential deleterious or contaminating substances.	No metallurgical or bulk density tests were conducted at the project by Prospech.
Further work	The nature and scale of planned further work (eg tests for lateral extensions or depth extensions or large-scale step-out drilling). Diagrams clearly highlighting the areas of possible extensions, including the main geological interpretations and future drilling areas, provided this information is not commercially sensitive.	Prospech may carry out drilling subject to resampling of these intervals in late April 2023.

Section 1 Appendix – Assays of Rare Earth Oxides to date collated from historic drilling.

HOLE_ID	SHORT	ID DEPTH FROM	рерти то	INT	La2O3_ppm	CeO2_ppm	Pr2O3_ppm	Nd2O3_ppm	Sm2O3_ppm	Eu2O3_ppm	Gd2O3_ppm	Tb2O3_ppm	Dy2O3_ppm	Ho2O3_ppm	Er2O3 ppm	Tm2O3 ppm	Yb2O3_ppm	Lu2O3_ppm	Y2O3_ppm	TREO	Hf_ppm	Nb ppm	Rb ppr	n 7
JOKIKANGAS-001	JO01	97.30	97.65	0.35	11.7	175.7	23.4	46.6	11.6	23.2	11,5	0.0	0.0	0.0	11.4	0.0	0.0	0.0	203.2	518	30.0	190.0	300.0	
OKIKANGAS-001	JO01	130.00	133.30	3.30	0.0	35.1	0.0	11.7	23.2	23.2	0.0	0.0	0.0	0.0	0.0	0.0	11,4	0.0	203.2	308	30.0	150.0	240.0	
OKIKANGAS-004	JO04	74.9	76.2	1.30	11.7	140.5	23.4	46.6	34.8	34.7	11.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	101.6	405	30.0	50.0	150.0	
OKIKANGAS-004 OKIKANGAS-004	.1004	76.4	77.4	1.00	11.7	128.8	23.4	46.6	34.8	34.7	11.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	101.6	393	30.0	50.0	180.0	
	0001	115.85	116.85		1,000	00000	018/67/	2007.02003	77.600	500000	100000	08090	U.5415	10000	1000	0.00	151045	17373	200000	2/22/2				
OKIKANGAS-004	JO04			1.00	11.7	128.8	11.7	58.3	23.2	23.2	11.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	114.3	383	20.0	60.0	170.0	
OKIKANGAS-004	JO04	117	118.6	1.60	0.0	128.8	11.7	46.6	23.2	46.3	11.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	101.6	370	30.0	60.0	160.0	
OKIKANGAS-004	JO04	179.8	180.8	1.00	46.9	222.5	35.1	93.3	34.8	34.7	23.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	127	617	30.0	90.0	210.0	
OKIKANGAS-004	JO04	180.95	181.95	1.00	23.5	152.2	11.7	58.3	34.8	46.3	23.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	127	477	20.0	60.0	200.0	
OKIKANGAS-005	JO05	80.95	81.95	1.00	0.0	152.2	11.7	46.6	104.4	104.2	80.7	34.5	34.4	11.5	68.6	0.0	0.0	0.0	152.4	801	10.0	120.0	200.0	
OKIKANGAS-005	JO05	82.07	83.5	1.43	0.0	140.5	11.7	46.6	92.8	92.6	69.2	23.0	11.5	0.0	22.9	0.0	0.0	0.0	127	638	0.0	70.0	200.0	
OKIKANGAS-005	JO05	178.3	179.3	1.00	23.5	187.4	35.1	58.3	92.8	92.6	57.7	11.5	0.0	0.0	68.6	11.4	0.0	0.0	12.7	652	10.0	60.0	230.0	
OKIKANGAS-005	JO05	179.75	180.7	0.95	0.0	163.9	23.4	46.6	81.2	81.1	57.7	11.5	0.0	0.0	22.9	0.0	0.0	0.0	114.3	603	10.0	40.0	230.0	
OKIKANGAS-011	JO11	54.10	54.30	0.20	93.8	234.2	35.1	93.3	232.0	208.4	196,0	115.1	114,8	11.5	365.8	91.4	57.0	79.6	177.8	2106	100.0	130.0	160.0	T
OKIKANGAS-012	JO12	26.90	27.10	0.20	23.5	187.4	23.4	93.3	69.6	34.7	46.1	0.0	68.9	22.9	194.3	0.0	0.0	0.0	939.8	1704	60.0	140.0	80.0	+
KIKANGAS-012	JO12	42.25	42.65	0.40	492.7	1124.2	140.4	466.4	243.6	162 1	253.7	92.1	183.7	11.5	182.9	79.9	68.3		939.8	4509	130.0	310.0	80.0	Ť
AND DESCRIPTION OF THE PARTY OF	100000000			20.00	0.00			100.1										68.2	222.2			10.1010		+
(IKANGAS-013	JO13	22.60	23.10	0.50	1255.1	2751.9	327.6	1131.0	313.2	92.6	369.0	34.5	195.2	0.0	22.9	0.0	34.2	0.0	1028.7	7556	940.0	710.0	120.0	
(IKANGAS-013	JO13	32.80	33.10	0.30	1642.2	3583.3	456.3	1539.1	475.6	196.9	541.9	126.6	321.4	0.0	45.7	91.4	113.9	0.0	1320.8	10455	1160.0	1640.0	80.0	4
TAJAKANGAS-0		73.200	74.200	1.000		187.4	93.6	151.6	23.2	11.6	46.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	50.8	599		80.0	200.0	
TAJAKANGAS-0		74.200	74.400	0.200		9438.3	1193.4	4092.7	823.6	57.9	1095.4	0.0	0.0	0.0	0.0	0.0	0.0	0.0	3441.7	24448		4700.0	60.0	
TAJAKANGAS-0		74.400	75.400	1.000		152.2	93.6	139.9	11.6	0.0	23.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	114.3	546		50.0	220.0	+
TAJAKANGAS-0		8.100	9.200			140.5	23.4	46.6	34.8	46.3	23.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	101.6	416	_	60.0	150.0	
ATAJAKANGAS-0		9,200	9.350			5655.9	690.3	2402.0	533.6	69.5	645.7	34.5	310.0	0.0	171.5	0.0	113.9	0.0	2197.1	15346		2980.0	120.0	
ATAJAKANGAS-0		9.350	10.850			222.5	23.4	70.0	34.8	57.9	23.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	127	582	- 1	100.0	180.0	
ATAJAKANGAS-0 ATAJAKANGAS-0		56.300	57.330			128.8	23.4	46.6	34.8	23.2	11.5	0.0	0.0	0.0	0.0	0.0	0.0	0.0	101.6	370		40.0	170.0	
ATAJAKANGAS-U ATAJAKANGAS-U		57.330	57.500			3278.8	421.2	1387.5	301.6	57.9	369.0	0.0		0.0	68.6	0.0	22.8	0.0	1155.7	8690 347		2030.0	100.0	
		57.500	58.500			128.8	23.4	46.6	23.2	23.2	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	101.6				170.0	
ATAJAKANGAS-0 ATAJAKANGAS-0		103.650 30.000	106.650 32.000			46.8 138.2	0.0 16.1	11.7 62.3	46.4 11.5	34.7 2.7	9.5	1.3	7.3	0.0	3.7	0.0	0.0 3.1	0.0	88.9 40.894	229 369	8.8	20.0 40.8	140.0	
ATAJAKANGAS-0		100.450				140.5	23.4	58.3	34.8	34.7	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	101.6	405	0.0	50.0	170.0	
ONTIOAHO-001	KO01	73.330	73.730			151.3	18.4	69.7	13.3	2.7	11.4	1.8	9.5	1.8	4.9	0.6	3.6	0.5	51.816	418	9.8	65.9	142.2	_
ONTIOAHO-001	KO01	78.200	81,700			11.7	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0	12	9.8	10.0	142.2	
ONTIOAHO-001	KO01	81.700	87.100			0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0	0		10.0	230.0	
ONTIOAHO-001	KO01	87.100	91,600	1,000,000		726.0	0.0	291.5	69.6	34.7	57.7	0.0	0.0	0.0	0.0	0.0	0.0	0.0	304.8	1566		370.0	320.0	
ONTIOAHO-001	KO01	104.450	108.250			690.9	0.0	268.2	81.2	34.7	69.2	0.0	23.0	0.0	0.0	0.0	0.0	0.0	317.5	1825		390.0	310.0	
ONTIOAHO-001	KO01	104.450	104.950	0.500		645.1	72.4	247.3	40.0	47	32.4	5.8	35.4	7.2	18.7	2.3	13.7	1.9	193,294	1665	28.6	238.4	371.7	
ONTIOAHO-001	KO01	110,950	112,950	7770000		714.3	0.0	326.5	81.2	34.7	69.2	0.0	23.0	0.0	0.0	0.0	0.0	0.0	431.8	1974	20.0	510.0	36b.0	
ONTIOAHO-001	KO01	131,250	131.820	0.570		432.5	49.9	174.0	30.4	3.7	27.6	4.5	27.0	5.5	15.0	1.9	10.8	1.5	161.417	1177	31.9	227.3	341.9	
NTIOAHO-001	KO05	13.000	13.350	0.350		125.3	15.2	58.0	10.0	2.3	8.4	1.2	6.8	1.4	3.7	0.5	3.2	0.5	38.735	338	9.0	49.0	106.7	-
ONTIOAHO-005	KO05	25,500	25.750			127.8	15.6	60.0	11.9	2.2	10.3	1.6	9.0	1.8	5.1	0.7	4.5	0.7	52.197	365	11.9	54.1	111.9	
ONTIOAHO-005	KO05	30.450	30,950	0.500		695.6	79.5	283.6	43.1	4.5	33.1	5.3	34.6	7.9	26.6	4.0	26.9	3.9	220.726	1822	85.2	460.7	385.2	
ONTIOAHO-005	KO05	58.300	58.800			463.0	52.0	181.3	30.9	3.7	28.5	4.5	27.2	5.6	15.7	2.2	14.2	2.0	146.05	1234	49.5	321.2	249.5	
ONTIOAHO-005	KO05	56.400	60.400			667.5	93.6	268.2	69.6	34.7	80.7	0.0	0.0	0.0	0.0	0.0	0.0	0.0	368.3	1899	40.0	470.0	380.0	
ONTIOAHO-005	KO05	60.400	62.400			796.3	105.3	291.5	58.0	11.6	57.7	0.0	23.0	0.0	0.0	0.0	0.0	0.0	457.2	2199	i	490.0	410.0	
ONTIOAHO-005	KO05	70.140	70.640			496.2	57.9	201.8	35.2	4.1	29.8	4.5	25.0	4.9	14.0	1.9	12.1	1.7	151,511	1296	33.6	248.3	368.8	
ONTIOAHO-005	KO05	117.000				205.3	25.2	89.1	14.9	1.8	13.4	2.3	14.5	2.9	8.8	1.2	7.5	1.2	88.265	591	18.7	132.2	226.4	
ONTIOAHO-006	KO06	30,000	30.310			127.1	15.5	59.6	10.3	2.4	8.4	1.2	6.1	1.2	3.3	0.5	3.2	0.4	35.814	339	12.3	39.2	158.0	Т
ONTIOAHO-006	KO06	31.000	35,000			210.8	35.1	93.3	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	165.1	539	1.0.0	100.0	160.0	
ONTIOAHO-006	KO06	44.000	44.460			533.9	63.0	228.4	38.5	5.1	34.3	5.5	32.7	7.2	22.0	3.2	20.8	2.9	209.169	1494	59.5	299.3	361.8	
ONTIOAHO-006	KO06	83.800	86.400		5.9	175.7	35.1	93.3	34.8	34.7	11.5	0.0	0.0	11.5	0.0	0.0	0.0	0.0	254	656		250.0	200.0	
ONTIOAHO-006	KO06	85.600	86.000			747.4	89.3	325.9	62.1	7.5	67.7	14.0	104.4	27.6	103.6	18.0	129.7	19.9	800.481	2865	510.4	660.7	261.3	
CONTIOAHO-006	KO06	96.000	99.000	3.000	258.1	538.7	70.2	209.9	69.6	46.3	57.7	0.0	0.0	0.0	0.0	0.0	0.0	0.0	228.6	1479		310.0	250.0	
ONTIOAHO-006	KO06	35.000	42.500	7.500	293.3	608.9	93.6	256.5	46.4	34.7	46.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	330.2	1710		400.0	310.0	
ONTIOAHO-006	KO06	42.500	48.000	5.500	246.3	538.7	70.2	221.5	58.0	34.7	46.1	0.0	0.0	0.0	0.0	0.0	0.0	0.0	317.5	1533		390.0	300.0	
ONTIOAHO-006	KO06	134.600	135.900	1.300	11.7	58.6	11.7	23.3	0.0	11.6	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0	50.8	168		40.0	60.0	
ONTIOAHO-006	KO06	147.430	147.860	0.430	35.5	66.3	7.6	28.2	4.8	0.7	4.2	0.6	3.8	0.8	2.4	0.3	2.4	0.4	22.86	181	2.8	45.4	96.8	
ONTIOAHO-007	KO07	27.100	31.100	4.000	504.4	1147.6	163.8	513.0	116.0	34.7	126.8	0.0	57.4	0.0	45.7	0.0	11.4	0.0	673.1	3394		550.0	280.0	Ī
ONTIOAHO-007	KO07	31.100	37.120	6.020	387.1	819.7	105.3	361.5	58.0	11.6	69.2	0.0	11.5	0.0	0.0	0.0	0.0	0.0	482.6	2306		420.0	320.0	
ONTIOAHO-007	KO07	36.100	36.600	0.500	462.0	904.7	108.6	393.2	74.3	9.1	66.7	10.3	58.6	11.4	31.8	4.2	25.5	3.4	317.627	2481	42.3	500.9	378.0	
ONTIOAHO-007	KO07	37.120	44.500	7.380	316.7	655.8	81.9	291.5	69.6	34.7	69.2	0.0	11.5	0.0	11.4	0.0	0.0	0.0	342.9	1885		420.0	290.0	
CONTIOAHO-007	KO07	44.500	52.700	8.200	363.6	761.2	93.6	314.8	92.8	34.7	69.2	0.0	34.4	0.0	11,4	0.0	0.0	0.0	381	2157	1	420.0	340.0	
CONTIOAHO-007	KO07	52.700	58.500	5.800	316.7	655.8	93.6	268.2	69.6	34.7	57.7	0.0	0.0	0.0	0.0	0.0	0.0	0.0	330.2	1826		340.0	320.0	
ONTIOAHO-007	KO07	58.500	60.050	1.550	199.4	409.9	46.8	174.9	58.0	34.7	46.1	0.0	0.0	0.0	22.9	0.0	0.0	0.0	317.5	1310	1	310.0	340.0	
ONTIOAHO-007	KO07	135.550	137.300	1.750	23.5	105.4	23.4	46.6	34.8	34.7	34.6	0.0	11.5	0.0	0.0	0.0	0.0	0.0	152.4	467	ĺ	200.0	140.0	
ONTIOAHO-007	KO07	168.570	169.000	0.430	246.9	493.5	62.5	243.1	48.5	6.0	44.9	7.2	41.1	8.1	22.4	2.9	17.4	2.4	228.727	1476	30.5	266.6	137.0	
CONTIOAHO-007	KO07	176.720	177.220	0.500		135.0	16.5	60.9	11.2	2.5	9.7	1.5	7.7	1.5	4.1	0.6	3.4	0.5	42.799	364	9.9	42.7	113.3	
CONTIOAHO-012	KO12	23.780	24.300	0.520		130.4	16.1	58.8	11.2	2.6	9.4	1.4	7.4	1.4	4.0	0.5	3.5	0.5	39.497	353	9,9	41.7	141.7	Ξ
CONTIOAHO-012	KO12	68.050	68.530	0.480		263.7	31.6	119.2	22.9	4.0	21.2	3.5	20.3	4.1	12.1	1.6	10.1	1.4	117.348	765	22.7	118.8	177.6	
ONTIOAHO-012	KO12	91.800	93.200	1.400	0.0	82.0	0.0	104.9	116.0	11.6	0.0	0.0	0.0	0.0	0.0	45.7	34.2	0.0	177.8	572		250.0	270.0	
	KO12	119,000	119,540	0.540		636.7	73.6	258.9	48.6	5.6	41.9	6.7	37.1	7.6	21.3	3.0	18.5	2.6	227.584	1726	43.7	315.1	387.1	

Continued next Page

Section 1 Appendix – Assays of Rare Earth Oxides to date collated from historic drilling (continued).

HOLE_ID	SHORT_ID D	DEPTH_FROM D	EPTH_TO IN	TV	La2O3_ppm	CeO2_ppm	Pr2O3_ppm	Nd2O3_ppm	Sm2O3_ppm	Eu2O3_ppm	Gd2O3_ppm	Tb2O3_ppm	Dy2O3_ppm	Ho2O3_ppm	Er2O3_ppm	Tm2O3_ppm	Yb2O3_ppm	Lu2O3_ppm	Y2O3_ppm	TREO	Hf_ppm	Nb_ppm		Zr_ppm
OTM11008	OT08	45.780	47.990	2.210		289.2	28.4	101.3	18.6	2.3	16.3	2.7	16.7	3.2	9.1	1.3	8.7	1.3	102.362	755	16.4	145	165.5	750
OTM11008	OT08	66.300	68.300	2.000		241.2	25.7	99.3	20.6	2.7	19.8	3.2	19.6	3.8	10.3	1.4	8.7	1.2	124.333	702	19.5	180.5	230.0	843
OTM11008	OT08	90.000	92.000	2.000		353.6	37.7	144.0	28.0	3.3	24.1	3.9	23.4	4.4	12.5	1.7	12.1	1.7	131.445	957	24.2	204	174.0	1090
OTM11009 OTM11009	OT09 OT09	28.030	29.030	0.500	76.7	175.7	17.1	66.7	12.9	2.6	11.1	1.7	10.1	1.8	5.0	0.7	4.6	0.6	57.277 708.66	445 2545	11.7	57.9 523	178.0 362.0	485 10900
OTM11009 OTM11009	0109	29.030	31,530	2.000	313.2 293.3	689.7 586.7	75.2 61.3	298.5	66.0	9.2	71.8 40.0	14.4	102.4 41.2	22.1	69.6	10.9	81.2	11.5	708.66 266.7	1635	50.4	289	362.0	2150
OTM11009	OT09	31.530	32.970	1.440		1610 1	163.8	609.8	109.3	13.2	91.3	15.4	96.1	18.3	49.6	5.9	32.8	3.9	506.73	4150	57.6	514	328.0	2620
OTM11009	OT09	32.970	34,400	1.430	432.8	839.6	85.8	317.2	57.5	7,1	50.2	7.8	47.1	8,9	25.0	3.5	23.6	3.3	267.97	2177	62.1	412	281.0	2780
OTM11009	ОТ09	34.400	35.020	0.620		466.1	48.9	186.0	37.0	4.7	31.4	5.0	30.2	5.6	15.5	2.0	12.8	1.8	187.96	1269	24.1	237	732.0	1240
OTM11009	ОТ09	35.020	37.020	2.000		738.9	75.5	271.7	47.2	5.5	38.0	6.1	36.9	7.0	19.3	2.5	16.3	2.2	224.79	1875	39.6	331	310.0	1800
OTM11009	ОТ09	37.020	39.020	2.000	415.2	785.7	80.6	289.2	50.8	6.1	42.2	6.5	38.3	7.1	19.4	2.6	17.3	2.4	230.505	1994	38.2	480	314.0	1600
OTM11009	ОТ09	39.020	39.380	0.360	543.1	1027.0	107.6	369.6	61.6	7.3	48.3	7.0	42.9	8.6	24.7	3.8	22.7	3.2	279.4	2557	44.0	457	284.0	1820
OTM11009	OT09	39.380	41.380	2.000	319.1	623.0	67.7	237.9	46.5	6.0	40.8	6.5	38.5	7.7	22.1	3.5	21.0	3.0	242.57	1686	51.8	371	296.0	2040
OTM11009	OT09	41.380	43.690	2.310	336.7	678.0	72.4	249.5	50.1	6.5	45.4	7.7	46.3	9.1	24.0	3.2	18.0	2.5	288.29	1838	43.6	317	327.0	1790
OTM11009 OTM11009	OT09	43.690 45.330	45.330 46.720	1.640	200.0	366.5 244.7	38.4 27.4	131.8 98.9	24.8	3.6	24.1	4.2 3.7	28.5	6.6 4.8	15.0	3.9	17.8	4.3	208.28 139.065	1093 749	167.5 76.0	229 169	275.0 364.0	6050 3550
OTM11009	OT09	46,720	48.580	1.860	185.9	366.5	39.8	141.7	26.3	3.9	21.5	3.0	15.8	3.0	8.4	1.3	8.5	1.4	95.504	923	60.5	201	243.0	2400
OTM11009	OT09	48,580	50.060	1.480	299.1	577.3	62.7	221.5	43.7	6.2	39.3	6.4	39.0	7.9	23.0	3.7	23.7	3.6	281.94	1639	83.9	379	263.0	3340
OTM11009	ОТ09	50.060	51.540	1.480	183.0	364.2	40.2	142.8	27.7	4.2	23.9	3.8	22.0	4.4	12.4	1.9	12.0	1.8	151.765	996	52.1	264	216.0	2000
OTM11009	ОТ09	51.540	51.850	0.310	41.4	94.3	11.6	43.7	8.6	1.8	6.6	0.9	5.0	0.9	2.6	0.4	2.4	0.3	33.909	254	9.1	37.5	312.0	358
OTM11009	ОТ09	51.850	52.340	0.490	486.8	850.1	86.1	274.0	39.1	4.9	24.8	3.1	15.4	2.7	7.2	1.1	6.2	0.9	92.075	1895	10.4	68.6	87.8	427
OTM11009	ОТ09	52.340	52.730	0.390		1698.0	169.7	551.5	78.6	9.0	51.8	7.4	41.8	8.5	25.9	4.3	25.4	3.3	312.42	3962	21.8	248	106.0	915
OTM11009	OT09	52.730	53.240	0.510		315.0	35.1	124.8	26.1	3.8	25.0	4.5	26.9	5.3	15.0	2.4	14.7	2.1	156.845	908	61.1	282	376.0	2240
OTM11009 OTM11009	OT09 OT09	53.240 54.060	54.060 56.060	2,000	205.9 287.4	432.1 560.9	48.3 62.4	174.3	36.9 41.2	5.1 5.3	34.6	5.9	35.2	7.0 5.2	19.8	3.2	19.4	2.8	203.2 162.56	1234	68.0 33.9	448	319.0 282.0	2620 1310
OTM11009 OTM11009	O109	63.000	65.000	2.000	163.0	330.2	37.2	225.0 134.1	41.2 26.2	3.3	33.4 23.2	4.8 3.7	26.9 21.4	4.3	14.3 12.1	1.9	13.3	2.0 1.9	136.525	911	57.8	256 216	406.0	2260
OTM11009	OT09	65.000	67.000	2.000		758.8	82.6	288.0	56.4	6.9	48.5	7.7	44.9	8.8	24.5	3.8	23.1	3.3	271.78	2028	64.8	507	411.0	2490
OTM11009	ОТ09	67.000	69.000	2.000		676.8	74.8	267.0	52.9	6.5	45.8	7.3	42.1	8.2	23.0	3.5	20.2	2.8	253.365	1830	50.0	387	277.0	2010
OTM11009	ОТ09	89.100	90.100	1.000	225.8	427.4	46.3	162.7	29.8	3.5	24.7	3.7	20.8	4.0	11.0	1.6	9.6	1.4	131.445	1104	33.8	219	281.0	1270
OTM11010	OT10	63.450	64.120	0.670	163.6	327.9	37.0	130.6	25.6	3.0	22.4	3.8	22.7	4.6	13.4	2.1	12.6	1.8	132.08	903	34.6	219	172.5	1400
OTM11010	OT10	64.120	66.120	2.000	191.2	381.7	41.4	144.0	25.6	2.8	19.8	3,1	17.8	3.6	10.5	1.7	10.9	1.6	106.045	962	33.6	175.5	152.5	1400
OTM11011	OT11	13.750	14.900	1.150		777.5	84.8	292.7	49.3	5.2	37.6	5.4	28.6	5.2	13.9	2.1	11.8	1.6	173.355	1855	21.2	120	230.0	882
OTM11011	OT11	14.900	15.900	1.000	194.7	391.1	43.6	152.7	25.4	2.6	19.0	2.7	15.3	2.9	8.2	1.3	7.9	1.2	94.107	963	21.8	111	235.0	856
OTM11011 OTM11011	OT11 OT11	15.900 17.450	17.450 19.450	1.550 2.000		435.6 473.1	51.2 53.4	183.6 186.0	38.4	4.2 3.6	33.3 25.9	5.8 4.0	35.4 21.8	7.0	20.0 10.3	3.2 1.5	18.4 8.2	1.2	189.23 118.364	1237	79.0 19.3	406 162	171.5 195.5	2530 779
OTM11011	OT11	19.450	21.450	2.000		393.5	43.5	152.2	26.9	2.9	21.2	3.2	17.5	3.2	8.5	1.2	6.9	1.0	106.68	985	19.3	123.5	195.0	816
OTM11011	OT11	21.450	23.200	1.750		358.3	40.5	141.7	25.3	2.5	18.7	2.8	15.8	3.0	8.2	1.3	7.6	1.1	94.361	899	24.6	145.5	210.0	881
OTM11011	OT11	23.200	25.200	2.000	246.3	509.4	58.1	207.0	36.3	3.7	28.5	4.1	22.3	4.2	11.3	1.7	10.2	1,4	128.905	1273	24.7	138	213.0	931
OTM11011	OT11	25.200	27.200	2.000	178.3	356.0	39.9	139.9	26.1	2.6	20.3	3.1	17.7	3.4	9.7	1.5	8.7	1.3	113.03	922	26.1	157	220.0	979
OTM11011	OT11	46.900	48.900	2.000	303.8	585.5	63.3	220.4	40.1	4.6	34.0	5.2	30.8	6.2	17.4	2.5	13.2	1.9	199.39	1528	46.2	275	256.0	1870
OTM11011	OT11	48.900	49.100	0.200		3700.4	293.7	708.9	65.8	6.1	31.2	5.1	30.7	6.7	21.0	3.5	20.6	3.0	214.63	7504	67.4	325	256.0	3510
OTM11011	OT11	49.100	51.100	2.000	361.3	678.0	72.5	253.0	47.0	5.4	38.0	6.1	35.4	7.0	19.8	3.1	17.8	2.6	215.9	1763	59.6	317	239.0	2440
OTM11011	OT11 OT11	56.000 68.300	58.000 70.500	2.000	273.3	524.6 354.8	56.4	205.8	37.1 31.6	4.4	30.1 30.4	4.8	27.8 33.4	5.7 7.2	15.0 19.7	2.1	12.7	1.9	167.64	1369	38.4	255 304	209.0	1590
OTM11011 OTM11012	OT12	6.600	8.000	2.200 1.400		298.6	39.5 31.4	112.8	18.9	2.5	14.0	5.4 2.3	12.9	2.7	6.9	2.8 1.0	6.3	1.0	203.835 79.883	749	63.1 14.6	107	196.0	2700 609
OTM11012	OT12	8.000	8.500	0.500	101.9	207.3	22.9	87.5	16.2	2.5	14.0	2.3	13.3	2.9	7.6	1.1	7.0	1.1	90.043	578	10.1	99.3	186.0	431
OTM11012	OT12	8.500	8.700	0.200		1762.4	187.2	694.9	132.2	16.2	105.8	17.1	96.2	18.8	46.7	6.4	35.7	4.9	595.63	4586	55.0	603	179.0	2360
OTM11012	OT12	8.700	9.650	0.950		263.5	28.8	108.4	20.1	2.7	16.2	2.5	13.5	2.7	6.6	1.0	6.2	1.0	77.724	682	17.0	133	153.0	681
OTM11012	OT12	9.650	10.650	1.000		155.2	17.0	64.5	11.4	1.8	9.1	1,4	8.3	1.8	4.7	0.7	4.8	0.8	52.578	413	10.4	54.8	169.0	432
OTM11012	OT12	10.650	11.330	0.680		296.3	32.6	120.1	20.0	2.9	14.2	2.1	11.1	2.2	5.7	0.9	5.9	1.0	66.548	733	10.6	71.2	177.0	448
OTM11012	OT12	11.330	11.750	0.420		20.0	2.5	10.5	2.6	0.5	2.4	0.4	2.4	0.5	1.3	0.2	1.5	0.3	13.208	66	1.4	54.6	220.0	42
OTM11012 OTM11012	OT12 OT12	11.750 14.750	14.750 17.750	3.000		123.5 575.0	12.9 63.6	47.0 240.2	8.3	1.4 6.7	6.4 38.9	1.0 6.5	5.9 37.1	1.2 7.2	3.2 18.1	0.5 2.5	3.3 14.7	0.6	38.227 184.785	322 1517	7.6 32.8	60.1	171.5	279 1330
OTM11012	OT12	17.750	20.050	2.300		121.2	14.2	240.2 55.4	48.5 10.1	2.3	7.7	1.2	6.8	1.4	3.7	0.6	3.8	0.7	41.656	330	6.7	59	138.5	268
OTM11012	OT12	20.050	21.000	0.950		145.2	16.6	64.7	12.1	3.1	9.4	1.5	8.4	1.7	4.4	0.7	4.0	0.6	55.626	401	6.1	90.6	206.0	256
OTM11012	OT12	21.000	21.670	0.670		229.5	27.4	108.6	20.6	5.1	16.8	2.6	14.9	3.1	8.3	1.2	7.5	1.1	108.458	655	4.7	160.5	162.0	208
OTM11012	OT12	21.670	22.680	1.010	92.9	186.8	21.3	81.3	14.7	3.9	10.5	1.6	9.1	1.8	4.7	0.7	4.3	0.7	54.737	489	9.6	119.5	176.0	371
OTM11012	OT12	22.680	24.680	2.000	69.8	135.3	15.3	58.9	10.5	4.2	8.1	1.2	6.9	1.4	3.5	0.5	3.1	0.5	43.815	363	4.9	65.2	152.0	204
OTM11012	OT12	44.000	46.000	2.000	220.5	468.4	51.9	192.4	32.0	4.7	20.2	3.0	16.1	3.1	7.7	1.2	8.0	1,4	83.439	1114	26.7	119	168.0	1070
OTM11012	OT12	46.000	48.000	2.000	81.2	166.9	19.3	75.3	13.8	2.8	10.5	1.7	9.3	1.9	4.9	0.7	4.9	0.8	56.515	451	8.5	80.8	163.5	349
OTM11012	OT12	70.000	70.750	0.750		140.5	16.3	64.1	12.6	3.0	10.0	1.6	9.3	1.9	5.1	0.8	4.7	0.8	62.23	402	5.3	77.8	166.5	207
OTM11012 OTM11012	OT12 OT12	70.750 71.440	71.440 71.640	0.690	49.5 120.8	101.4 242.4	11.9	47.7 94.0	9.6	1.6	8.0 9.1	1.3	7.2 7.4	1.5	4.1	0.7	5.7 4.4	0.8	44.704 39.37	296 568	8.2 27.2	68.9 275	171.0	323 1070
OTM11012	OT12	71.640	72.440	0.800	75.0	152.8	17.6	68.1	12.8	2.5	9.7	1.5	8.7	1.8	4.7	0.7	4.7	0.8	53.34	415	11.7	122.5	154.0	451
OTM11012	OT12	72.440	72.750	0.310		134.7	14.7	56.2	9.7	2.5	7.0	1.1	5.9	1.2	2.9	0.4	2.3	0.4	36.957	350	2.9	133	552.0	120
OTM11012	OT12	72.750	74.080	1.330		161.6	18.4	69.5	12.8	2.8	9.8	1.6	9.4	2.0	5.3	0.8	5.7	1.0	59.944	439	22.2	174	139.0	816
OTM11012	OT12	74.080	74.370	0.290	96.4	196.1	22.1	83.3	15.2	2.0	11.1	1.8	10.3	2.2	6.2	1.0	7.6	1.4	71.755	528	45.5	195	129.5	1320
OTM11012	OT12	74.370	76.370	2.000	75.2	153.4	17.6	68.8	13.3	2.8	10.8	1.8	10.5	2.1	5.5	0.8	5.0	0.8	59.055	427	11.8	93.1	118.5	446
OTM11012	OT12	76.370	78.370	2.000	235.8	480.1	52.2	191.2	31.1	4.8	18.7	2.8	15.1	3,0	7.5	1.1	6.9	1.1	87.63	1139	20.7	93.8	135.0	739
OTM11012	OT12	108.000	109.580	1.580		142.3	17.1	69.0	13.3	2.8	9.5	1.5	8.7	1.8	4.8	0.7	4.7	0.8	54.991	399	7.1	89.7	134.0	279
OTM11012	OT12	111.950	112.240	0.290	63.2	135.8	16.2	63.3	11.7	2.2	8.2	1.3	7.5	1.5	4.1	0.6	4.2	0.7	43.307	364	8.7	86.5	129.5	340