

# Assays Confirm High-Grade Manganese Discovery at Wandanya

## Highlights

- Significant high-grade manganese assays received for the W2 prospect<sup>1</sup>, Wandanya located 80 km south of the Woodie Woodie Manganese Mine including:
  - **5m @ 33.2% Mn** from 4m including **2m @ 48.7% Mn** (WDRC032)
  - **5m @ 33.2% Mn** from 1m including **2m @ 44.1% Mn** (WDRC031)
  - **5m @ 32.4% Mn** from 4m including **2m @ 39.6% Mn** (WDRC027)
  - **6m @ 27.7% Mn** from 3m including **2m @ 42.9% Mn** (WDRC013)
- The stratabound mineralisation shows remarkable thickness and grade consistency over 240m of drilled strike and remains open to the east and north where the Company has mapped 1.75km of intermittent high grade outcropping manganese
- W2 is interpreted as stratabound, fault related hydrothermal manganese enrichment representing a significant new exploration model on the eastern margin of the Oakover Basin.
- Metallurgical testwork planned to produce a high-grade Mn concentrate as a feedstock for alloying or high purity manganese sulphate (HPMSM)

Australian manganese explorer and developer, Black Canyon Limited (**Black Canyon** or **the Company**) (ASX: BCA) is pleased to announce the expedited laboratory-based assay results from the W2 prospect Reverse Circulation (RC) drill program. The maiden drill program identified high-grade hydrothermal related stratabound manganese mineralisation with these assay results confirming the initial pXRF results<sup>2</sup>

### **Black Canyon's Managing Director Brendan Cummins said:**

*"The laboratory-based assay results have confirmed the significant high-grade intercepts for the W2 prospect. I am impressed by the consistency of the grades and thickness of the manganese horizon we have discovered and the higher-grade intervals over 40% Mn. What is really appealing about this target from an exploration and resource delineation perspective is the benefit of a consistent mineralised horizon that is also associated with hydrothermal grades. I am excited by the upside of this new style of mineralisation as we plan our follow-up exploration programs to assess 1.75km of strike to the north and the potential of the manganese horizon to extend to the east."*

### Contact

35 Richardson Street West Perth, WA, 6005  
T +61 8 9426 0666  
E [info@blackcanyon.com.au](mailto:info@blackcanyon.com.au)  
W [www.blackcanyon.com.au](http://www.blackcanyon.com.au)

### Capital Structure (ASX: BCA)

Shares on Issue	81.8M
Top 20 Shareholders	47%
Board & Management	9%
Funds & Institutions	15%

### Board of Directors

**Graham Ascough**  
Non-Executive Chairman

**Brendan Cummins**  
Managing Director


**Simon Taylor**  
Non-Executive Director

**Adrian Hill**  
Non-Executive Director

### Balfour Manganese Field Highlights

Global MRE of 314Mt @ 10.5% Mn. \*  
Largest Resource in Western Australia.  
Development Options – Traditional Mn concentrate or HPMSM processing for EV's.

\*BCA Announcement 12/12/23

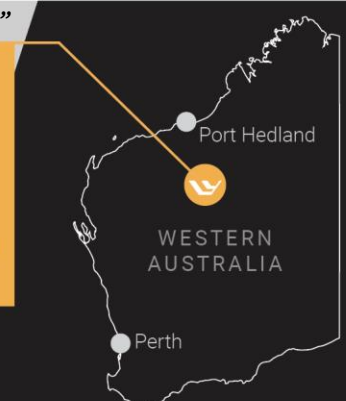

For personal use only



*Figure 1. W2 Prospect, RC drill bags from WDRC031 in the foreground*

## W2 Prospect, Wandanya (BCA 100%)

The W2 prospect was drilled on an approximate 40 x 40m grid testing a 240 long x 200m wide target. This drill program comprised 35 holes for 642m of drilling. Drill collar information is presented in Appendix 2.

### Expedited Assay Results

Initially, six RC holes were sampled for expedited assays, generating 38 one metre interval samples that were gathered along the eastern boundary of the stratabound mineralisation. Representative holes were sampled from every second line along the drilled strike of 240m. On each drill line, the last two eastern holes were sampled from depths between 4m and 9m, which included stratabound mineralisation and portions of the lower grade footwall and hangingwall.

The results are presented in Table 1, which show consistent zones of mineralisation with the bottom 2m for each intersection typically returning high grade mineralisation potentially suitable for direct shipping (DSO).

*Table 1. Assay results from WDRC12, 13, 26, 27, 31 and 32*

HOLE ID	FROM (m)	TO (m)	THICKNESS (m)	Mn (%)	Fe (%)	Drill intersection
WDRC013	3	9	6	27.4	2.7	6m @ 27.7 % Mn & 2.7% Fe from 3m, including 2m @ 42.9 % Mn from 6m
WDRC026	0	3	3	31.7	3.0	3m @ 31.7% Mn & 3.0 % Fe from surface
WDRC027	4	9	5	32.4	4.4	5m @ 32.4% Mn & 4.4% Fe from 4m, including 2m @ 39.6 % Mn from 7m
WDRC031	1	6	5	33.2	2.6	5m @ 33.2% Mn & 2.6% Fe from 5m, including 2m @ 44.1% Mn from 4m
WDRC032	4	9	5	33.2	1.7	5m @ 33.2% Mn & 1.7% Fe from 4m, including 2m @ 48.7% Mn from 7m

The remainder of the RC assay results from the W2 drill program are expected in mid-November.

Manganese mineralisation was logged on the second and last holes on the eastern boundary of the drill pattern and remains open to the north, south and east. (Figure 2 & 3).

Sufficient sample has also been collected to undertake benchtop heavy liquid separation testwork to beneficiate lower grade manganese intervals, to determine if a 35 to 40% Mn product can be produced. This is particularly relevant for the mixed Mn/Dolomite breccia zone (Figure 4). Beneficiated ores could be sold to smelters for manganese alloying or as a high grade feedstock for HPMSM

Further details are provided in Appendix 1 and assay and pXRF results presented in Appendix 3

For personal use only

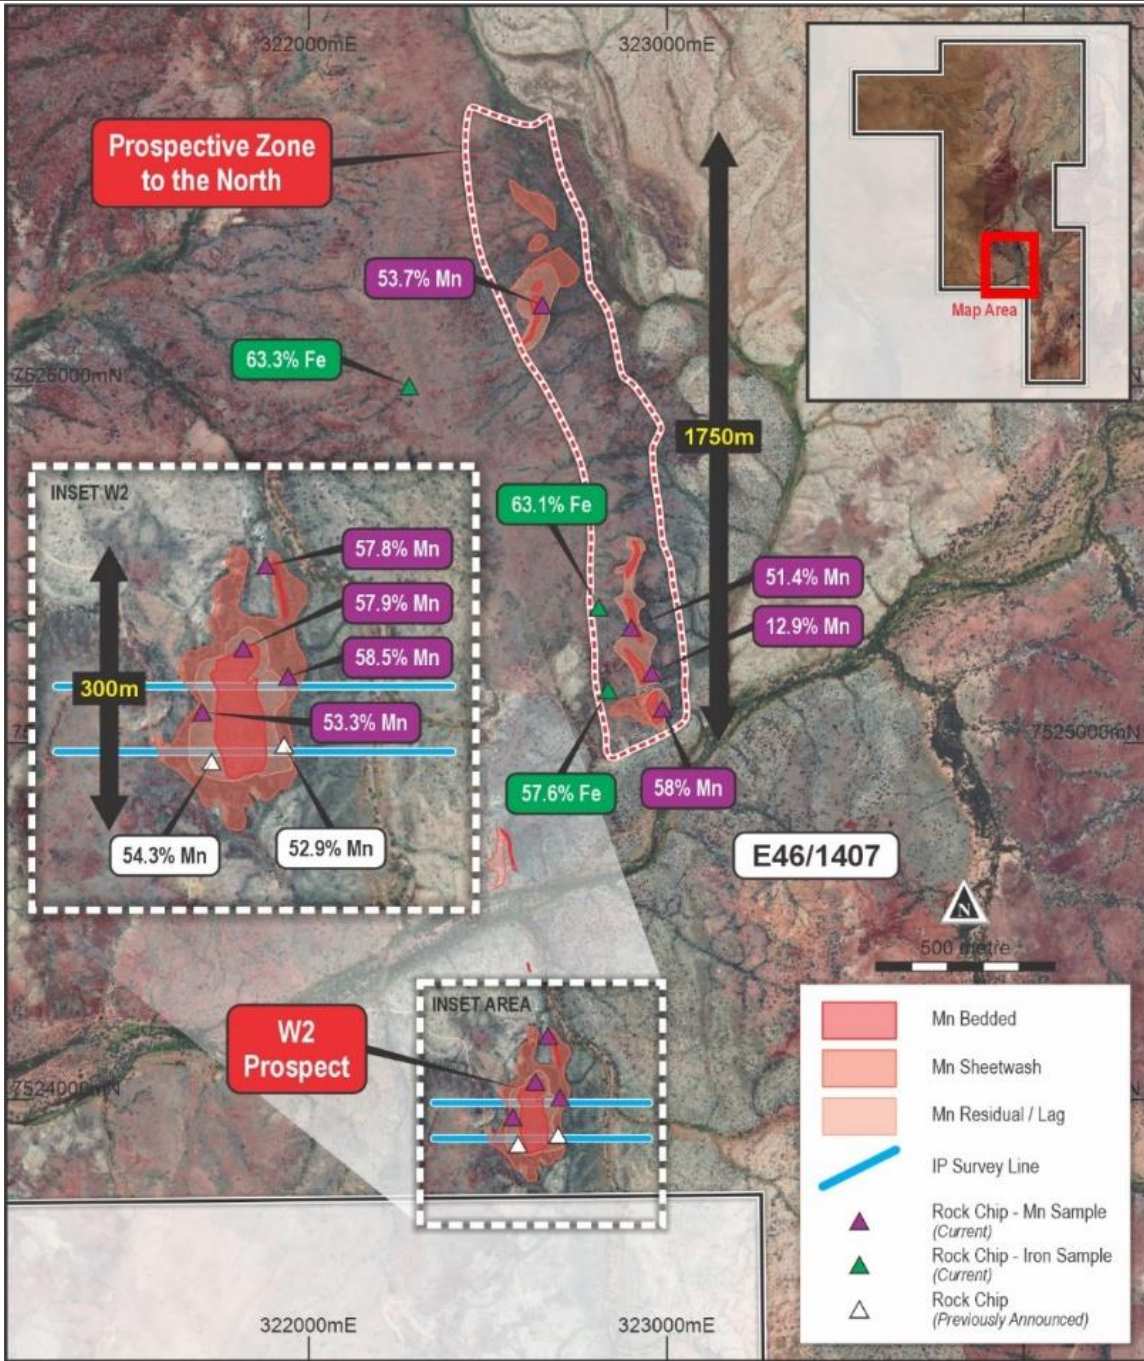
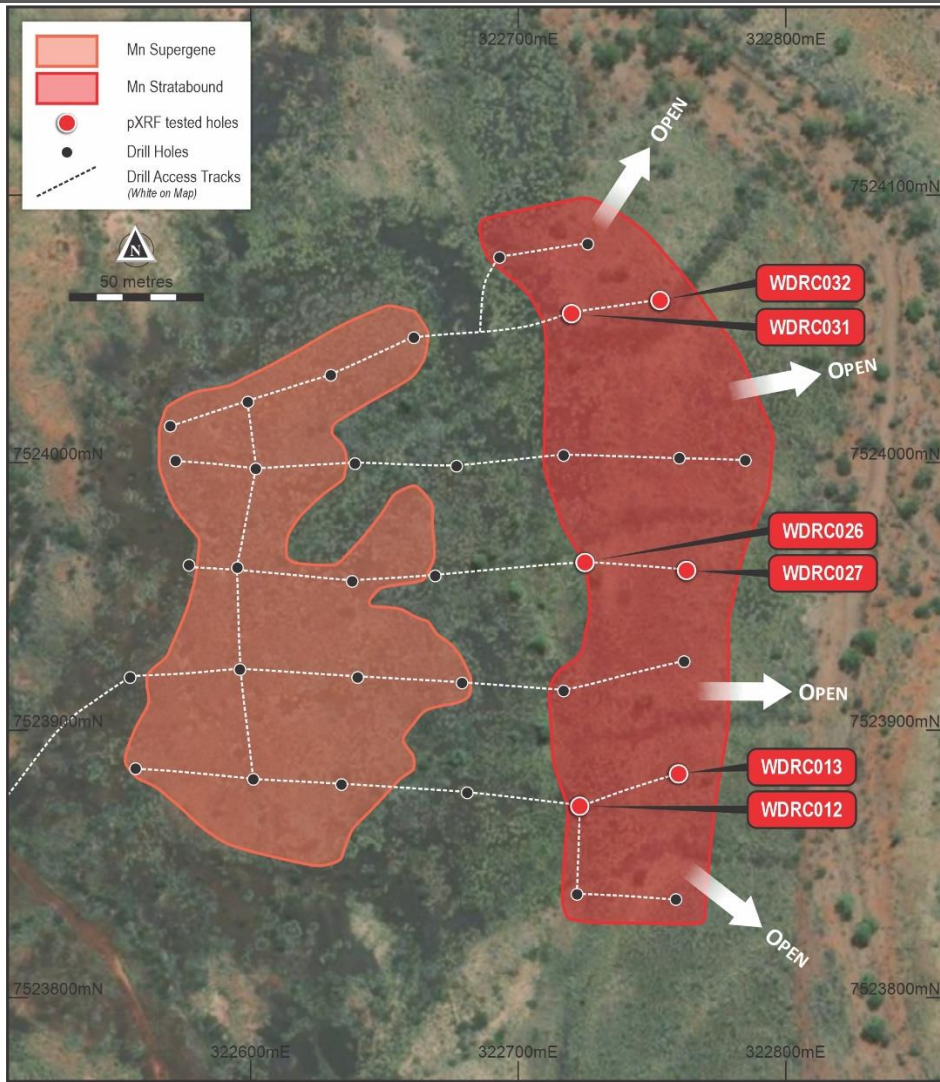


Figure 2. W2 prospect, Wandanya Project (E46/1407) showing high grade manganese outcrops and the IP survey lines



**Figure 3. Drill collar location plan and stratabound mineralisation projected to surface.**

For personal use only

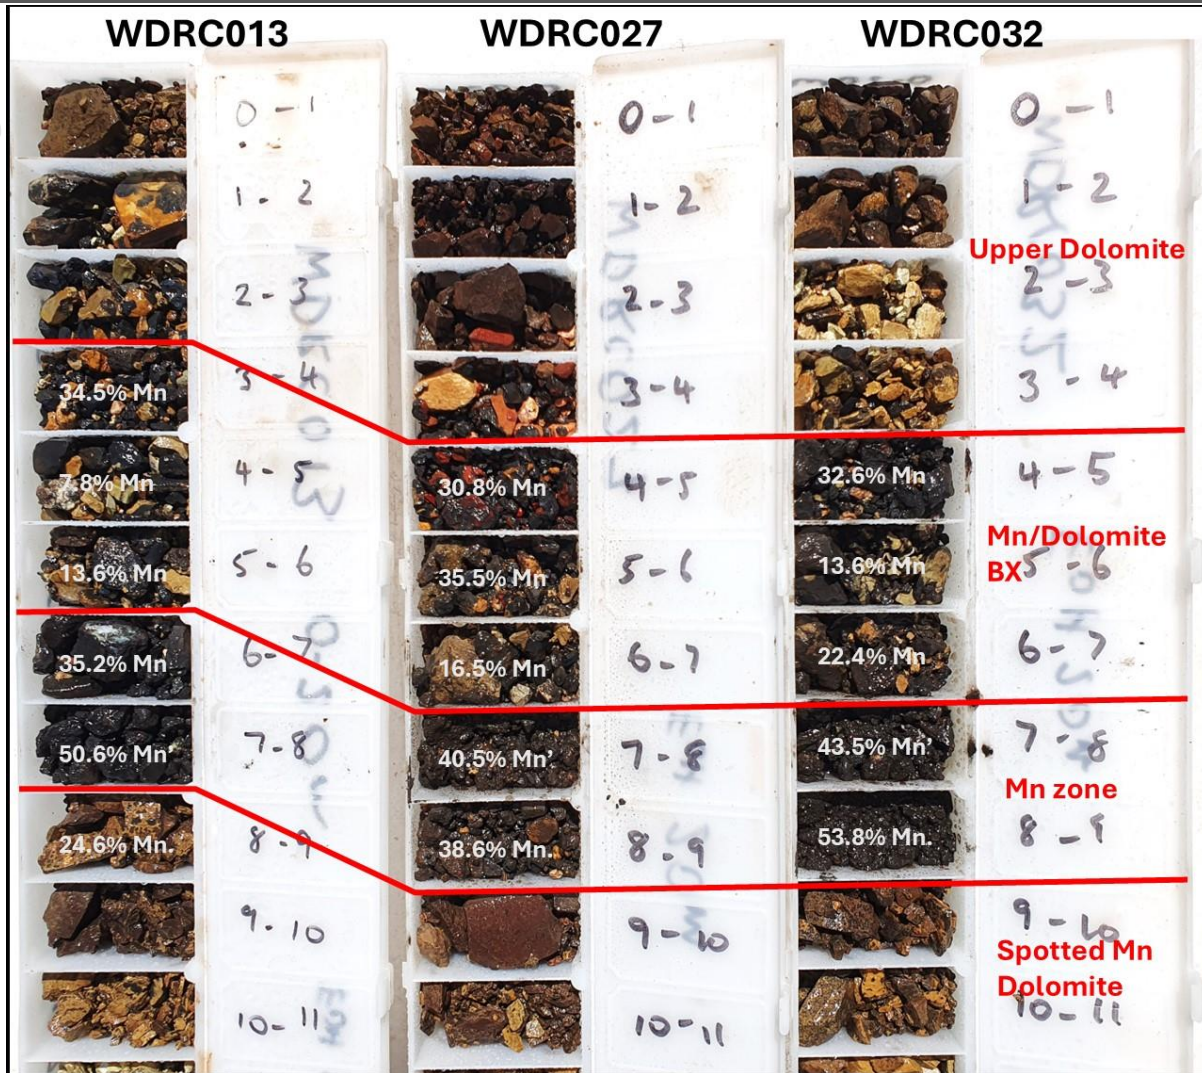


Figure 4. Chip tray photos from 0-11m from selected holes drilled into the W2 Prospect showing laboratory based assay result and various zones defined within the manganese horizon.

-END-

For personal use only

**This announcement has been approved by the Board of Black Canyon Limited.**

For further details:

**Brendan Cummins**  
**Managing Director**

Telephone: +61 8 9426 0666

Email: [brendan.cummins@blackcanyon.com.au](mailto:brendan.cummins@blackcanyon.com.au)

For media and broker enquiries:

**Andrew Rowell / Jason Mack**  
**White Noise Communications**


Telephone: +61 8 6374 2907

Email: [andrew@whitenoisecomms.com](mailto:andrew@whitenoisecomms.com)  
[jason@whitenoisecomms.com](mailto:jason@whitenoisecomms.com)

### Reference List:

1. ASX Announcement 14 November 2023 – Multiple high grade Manganese rock chip samples from Wandanya Project
2. ASX Announcement 27 September 2024 – High Grade Manganese Discovered at Wandanya.

### About Black Canyon

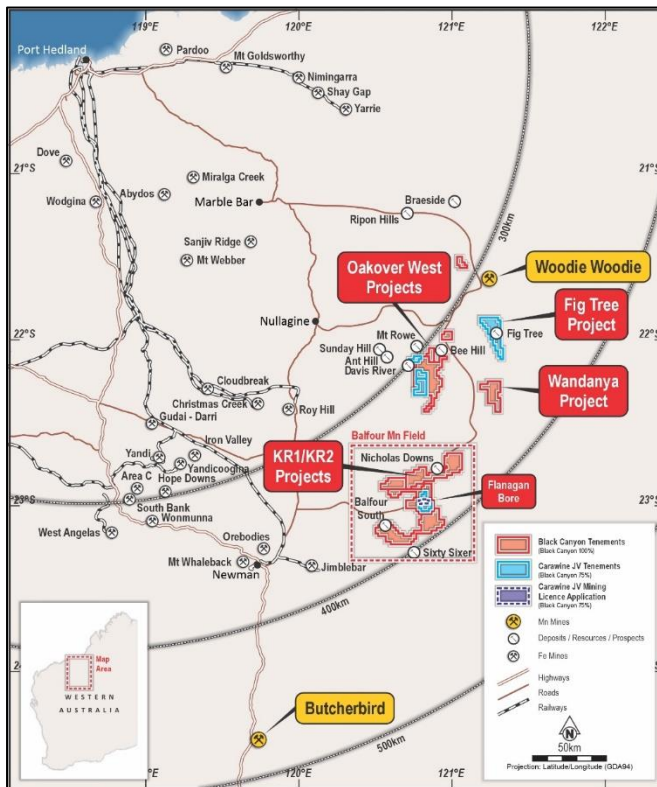

Black Canyon has consolidated a significant land holding totalling 2,100km<sup>2</sup> in the underexplored Balfour Manganese Field and across the Oakover Basin, in Western Australia.

The emerging potential for the Balfour Manganese Field is evident by the size of the geological basin, mineral resources identified to date, distance from port, potential for shallow open pit mining and a likely beneficiated Mn oxide concentrate product grading between 30 and 33% Mn. Black Canyon holds several exploration licenses 100% within the Balfour Manganese Field along with a 75% interest in the Carawine Joint Venture with ASX listed Carawine Resources Limited. A Global Mineral Resource (Measured, Indicated & Inferred) of 314 Mt @ 10.4% Mn has been defined across the Balfour Manganese Field projects.

Manganese continues to have attractive long-term fundamentals where it is essential and non-substitutable in the manufacturing of alloys for the steel industry and a critical mineral in the cathodes of Li-ion batteries.

## **Compliance Statements**

### Reporting of Exploration Results and Previously Reported Information

The information in this report that relates to Exploration Results is based on, and fairly represents, information and supporting documentation reviewed by Mr Brendan Cummins, Managing Director of Black Canyon Limited. Mr Cummins is a member of the Australian Institute of Geoscientists, and he has sufficient experience which is relevant to the style of mineralisation and type of deposits under consideration and to the activity which has been undertaken to qualify as a Competent Person as defined in the 2012 Edition of the “Australasian Code for Reporting of Exploration Results, Mineral Resources and Ore Reserves”. Mr Cummins consents to the inclusion in this release of the matters based on the information in the form and context in which they appear. Mr Cummins is a shareholder of Black Canyon Limited.

For further information, please refer to ASX announcements dated 17 May 2021, 10 June 2021, 7 July 2021, 15 July 2021, 5 October 2021, 4 January 2022, 8 February 2022, 21 February 2022, 2 March 2022, 23 March 2022, 13 April 2022, 9 June 2022, 7 September 2022, 15 September 2022, 11 October, 21 & 24 November 2022, 5 December 2022, 28 December 2022, 14 February 2023, 27 March 2023, June 1 2023, June 14 2023, June 17 2023, July 14 2023, 23 August 2023, 5 September 2023, 26 September 2023, 12 October 2023, 27 November 2023, 12 December 2023, 26 March 2024, and 1 May 2024, 2 July 2024, 21 August 2024, 25 September 2024 and 27 September 2024 which are available from the ASX Announcement web page on the Company’s website. The Company confirms that there is no new information or data that materially affects the information presented in this release that relate to Exploration Results and Mineral Resources in the original market announcements.

For personal use only

**APPENDIX 1: JORC 2012: TABLE 1**

Section 1 Sampling Techniques and Data		
Criteria	Explanation	Comment
Sampling techniques	<p><i>Nature and quality of sampling (eg cut channels, random chips, or specific specialised industry standard measurement tools appropriate to the minerals under investigation, such as down hole gamma sondes, or handheld XRF instruments, etc). These examples should not be taken as limiting the broad meaning of sampling.</i></p> <p><i>Include reference to measures taken to ensure sample representivity and the appropriate calibration of any measurement tools or systems used.</i></p> <p><i>Aspects of the determination of mineralisation that are Material to the Public Report. In cases where 'industry standard' work has been done this would be relatively simple (eg 'reverse circulation drilling was used to obtain 1 m samples from which 3 kg was pulverised to produce a 30 g charge for fire assay'). In other cases more explanation may be required, such as where there is coarse gold that has inherent sampling problems. Unusual commodities or mineralisation types (eg submarine nodules) may warrant disclosure of detailed information.</i></p>	<p><i>Reverse circulation ('RC') was used as the primary drilling technique for the projects.</i></p> <p><i>RC cuttings were continuously sampled at 1 m intervals. All drill holes were sampled and logged from surface to end of hole or depth of mineralisation.</i></p> <p><i>Drilling completed by Black Canyon has been used for the projects.</i></p> <p><i>All drill samples were logged for weathering, colour, lithology and mineralogy.)</i></p> <p><i>RC samples were collected and placed in marked green plastic bags in order at each collar position.</i></p> <p><i>The 1m interval samples are considered industry standard and representative of the material being tested.</i></p> <p><i>There was limited water encountered during the drill program.</i></p> <p><i>1m intervals were sampled using a shovel to firstly mix the sample in the green RC bag and then 3 – 4 spears of the shovel into the RC bag of sample which was then transferred to the numbered calico bag</i></p> <p><i>The drilling and sample techniques are considered representative for the style of mineralisation utilising 1m sample intervals</i></p>
Drilling techniques	<p><i>Drill type (eg core, reverse circulation, open-hole hammer, rotary air blast, auger, Bangka, sonic, etc) and details (eg core diameter, triple or standard tube, depth of diamond tails, face-sampling bit or other type, whether core is oriented and if so, by what method, etc).</i></p>	<p><i>Black Canyon drilling was completed using RC technique at 90-degree angle to collect 1 m samples as RC chips. Drill diameter is 5.25 inches as per standard RC sizing. A face sampling hammer was used to drill and sample the holes.</i></p> <p><i>The Company contracted Impact Drilling for the September 2024 drill campaign.</i></p>

For personal use only



For personal use only

<p><i>Drill sample recovery</i></p>	<p><i>Method of recording and assessing core and chip sample recoveries and results assessed.</i></p> <p><i>Measures taken to maximise sample recovery and ensure representative nature of the samples.</i></p> <p><i>Whether a relationship exists between sample recovery and grade and whether sample bias may have occurred due to preferential loss/gain of fine/coarse material.</i></p>	<p><i>The 2024 drill campaign recorded satisfactory drill sample recovery. The sample weights were not recorded on site, but the samples were weighed once received at the laboratory. The samples weights show good overall recoveries with smaller samples weights recorded in the top 1-2m.</i></p> <p><i>During the 2024 drill program the 1m samples were collected from a levelled cone splitter affixed to the side of the drill rig.</i></p> <p><i>It is unlikely the lower weights encountered in the top 1 - 2m of the holes has biased the samples particularly with the style of mineralisation.</i></p> <p><i>The samples were drilled mostly dry minimising sample bias</i></p>
<p><i>Logging</i></p>	<p><i>Whether core and chip samples have been geologically and geotechnically logged to a level of detail to support appropriate Mineral Resource estimation, mining studies and metallurgical studies.</i></p> <p><i>Whether logging is qualitative or quantitative in nature. Core (or costean, channel, etc) photography.</i></p> <p><i>The total length and percentage of the relevant intersections logged.</i></p>	<p><i>Geological logs exist for the September 2024 drill program.</i></p> <p><i>Logging of individual 1 metre intervals was completed using logging code dictionary which recorded weathering, colour, lithology and observed commentary to assist with determining manganese mineralisation.</i></p> <p><i>Logging and sampling has been carried out to industry standards.</i></p> <p><i>Drill holes were geologically logged in their entirety and a reference set of drill chips were collected in 20m interval chip trays for the drill program. The chip trays were all photographed on site at the end of drilling each hole.</i></p> <p><i>All metres drilled were logged</i></p>

For personal use only

<p><i>Sub-sampling techniques and sample preparation</i></p>	<p><i>If core, whether cut or sawn and whether quarter, half or all core taken.</i></p> <p><i>If non-core, whether riffled, tube sampled, rotary split, etc and whether sampled wet or dry.</i></p> <p><i>For all sample types, the nature, quality and appropriateness of the sample preparation technique.</i></p> <p><i>Quality control procedures adopted for all sub-sampling stages to maximise representivity of samples.</i></p> <p><i>Measures taken to ensure that the sampling is representative of the in-situ material collected, including for instance results for field duplicate/second-half sampling.</i></p> <p><i>Whether sample sizes are appropriate to the grain size of the material being sampled.</i></p>	<p><i>The samples were gather by using a shovel to mix the sample in the plastic bag and then spearing the shovel into each bag 3 to 4 times to gather the sample volume. These samples were all dry and a total of 3 to 5kg of samples was collected from each metre interval.</i></p> <p><i>The samples were submitted to Bureau Veritas who dried the sample for 12 hrs, crushed the entire sample to -10mm and then split of 1kg for pulverization to 95% passing 75um.</i></p> <p><i>The samples were taken dry.</i></p> <p><i>The sub sampling technique and quality control procedures is considered appropriate to ensure sample representivity.</i></p> <p><i>The sample size is considered appropriate for the grainsize and style of mineralisation</i></p> <p><i>No standards were inserted within this small sample batch.</i></p>
<p><i>Quality of assay data and laboratory tests</i></p>	<p><i>The nature, quality and appropriateness of the assaying and laboratory procedures used and whether the technique is considered partial or total.</i></p> <p><i>For geophysical tools, spectrometers, handheld XRF instruments, etc, the parameters used in determining the analysis including instrument make and model, reading times, calibrations factors applied and their derivation, etc.</i></p> <p><i>Nature of quality control procedures adopted (eg standards, blanks, duplicates, external laboratory checks) and whether acceptable levels of accuracy (ie lack of bias) and precision have been established.</i></p>	<p><i>The samples were submitted to Bureau Veritas in Canningvale, WA.</i></p> <p><i>The 3 – 5kg samples were weighed and dried prior to pulverising 100% of the sample for 95% passing 75µm.</i></p> <p><i>The sample was then analysed using method XF103 for manganese ores using fusion disc XRF for Fe, SiO<sub>2</sub>, Mn, Al<sub>2</sub>O<sub>3</sub>, TiO<sub>2</sub>, P<sub>2</sub>O<sub>5</sub>, S, MgO, K<sub>2</sub>O, Na<sub>2</sub>O, CaO, BaO and Cr<sub>2</sub>O<sub>3</sub>.</i></p> <p><i>Loss on Ignition (LOI) was also measured by Thermo Gravimetric Analysis (TGA)</i></p> <p><i>Bureau Veritas has undertaken its own internal QAQC checks using CRM, Blanks and pulp duplicates and no issues have been reported or identified.</i></p> <p><i>The CP is satisfied that the analysis was completed to an acceptable standard in the context in which the results have been reported</i></p>

For personal use only

<p><i>Verification of sampling and assaying</i></p>	<p><i>The verification of significant intersections by either independent or alternative company personnel.</i></p> <p><i>The use of twinned holes.</i></p> <p><i>Documentation of primary data, data entry procedures, data verification, data storage (physical and electronic) protocols.</i></p> <p><i>Discuss any adjustment to assay data.</i></p>	<p><i>Validation of the drilling files (collar, assay and lithology) was undertaken with field and data entry cross checks</i></p> <p><i>Adjustment of elemental oxides to primary element was completed using well known conversion factors.</i></p> <p><i>There were no twin holes</i></p> <p><i>There has been no adjustment to the assay data</i></p>
<p><i>Location of data points</i></p>	<p><i>Accuracy and quality of surveys used to locate drill holes (collar and down-hole surveys), trenches, mine workings and other locations used in Mineral Resource estimation.</i></p> <p><i>Specification of the grid system used.</i></p> <p><i>Quality and adequacy of topographic control.</i></p>	<p><i>All drill holes in the project area were surveyed by handheld GPS with an accuracy of +/-5 m. The accuracy of the location of the drill collars is sufficient at this stage of exploration and resource development.</i></p> <p><i>Grid system used is WGS 84 / UTM zone 51S.</i></p>
<p><i>Data spacing and distribution</i></p>	<p><i>Data spacing for reporting of Exploration Results.</i></p> <p><i>Whether the data spacing, and distribution is sufficient to establish the degree of geological and grade continuity appropriate for the Mineral Resource and Ore Reserve estimation procedure(s) and classifications applied.</i></p> <p><i>Whether sample compositing has been applied.</i></p>	<p><i>The 2024 drilling completed at W2 was conducted via a conventional drill grid. The nominal drill spacing was 40 m along east-west traverses and each traverse was spaced approximately 40 m apart north-south. The drill spacing was sufficient to establish grade and geological continuity.</i></p> <p><i>No sample compositing has been applied.</i></p>
<p><i>Orientation of data in relation to geological structure</i></p>	<p><i>Whether the orientation of sampling achieves unbiased sampling of possible structures and the extent to which this is known, considering the deposit type.</i></p> <p><i>If the relationship between the drilling orientation and the orientation of key mineralised structures is considered to have introduced a sampling bias, this should be assessed and reported if material.</i></p>	<p><i>At W2 drill lines were oriented east-west across the strike of the primary mineralisation trend. The drill holes were completed at 90 degrees (vertical).</i></p> <p><i>The mineralisation is relatively flat lying exhibiting a gentle dip to the east at W2.</i></p> <p><i>The drill grid is assumed to be located both perpendicular to the planar orientation of the key mineralised horizon with no or limited bias introduced with respect to the strike or dip of the mineralised horizon.</i></p>

Sample security	The measures taken to ensure sample security.	The samples were collected and transported by Company staff from site to the laboratory and also picked up by Company staff.
Audits or reviews	The results of any audits or reviews of sampling techniques and data.	No audits or reviews have taken place on the sampling techniques or data

**Section 2 Reporting of Exploration Results**

Criteria	Explanation	Comment
Mineral tenement and land tenure status	<p>Type, reference name/number, location and ownership including agreements or material issues with third parties such as joint ventures, partnerships, overriding royalties, native title interests, historical sites, wilderness or national park and environmental settings.</p> <p>The security of the tenure held at the time of reporting along with any known impediments to obtaining a licence to operate in the area.</p>	<p>The W2 mineralisation is located within E46/1407 held 100% by Black Canyon Ltd. Tenement E47/1407 was granted on the 11/04/2022 and expires on 10/04/2027</p> <p>The tenement upon which W2 is located are subject to a native title agreement with the Karlka Nyiyaparli Aboriginal Corporation. Archaeologic and Ethnographic heritage surveys have been completed on the W2 deposits which has enabled the drilling to be completed. Further Heritage surveys will be required to continue ground disturbing activities beyond the current drill areas.</p> <p>There are no other known impediments to obtaining a licence to operate in the area.</p>
Exploration done by other parties	Acknowledgment and appraisal of exploration by other parties.	<p>No other historic exploration has been completed on the tenement for manganese on E46/1407.</p> <p>For W2 Black Canyon completed a ground reconnaissance exercise in 2023 to map the manganese enrichments and determine down dip upside. The exercise proved significant manganese enrichment throughout the project areas both as outcropping, sub-cropping and as substantial float material. The early reconnaissance groundwork by Black Canyon was used as a basis for the 2023 DDIP survey and 2024 RC drilling programme.</p>
Geology	Deposit type, geological setting and style of mineralisation.	<p>The mineralisation model at W2 is preliminary but it appears to be a fault related hydrothermal stratabound deposit. There may be a supergene overprint to the original hydrothermal mineralisation.</p> <p>The mineralisation is located within a sedimentary sequence. From the base to the top of the sequence the geology comprises footwall dolomite, spotted manganese dolomite, massive manganese and manganese dolomite breccia overlain by hangingwall dolomite. The consistency of the mineralisation down dip and along strike has been interpreted to represent fault related, hydrothermal stratabound style of manganese mineralisation. Goethite alteration is common above the manganese zone and hematite was logged within the mineralised zones as jaspilitic bands. Manganese intensity increases towards the base of the sequence.</p>

For personal use only

For personal use only

Criteria	Explanation	Comment
		<p><i>The overall geological sequence is dipping very shallowly to the east but is also openly folded with a northerly axial plane forming undulating outcrops. Several large north-easterly faults can be identified along strike associated with surface mineralisation.</i></p> <p><i>The lithological sequence of the W2 prospect principally consists of the overlying Enachedoong Formation carbonates overlying the Stag Arrow Formation sediments from the Proterozoic Manganese Group of the southern Oakover Basin. The mineralisation style at W2 is stratabound and maybe associated with hydrothermal fluids replacing a suitable reactive host work at the base of the Enachedong Formation. Faults and structure are considered important features of this style of mineralisation with multiple north east trending faults visible from surface imagery.</i></p>
<p><i>Drill hole Information</i></p>	<p><i>A summary of all information material to the understanding of the exploration results including a tabulation of the following information for all Material drill holes:</i></p> <ul style="list-style-type: none"> <li><i>• easting and northing of the drill hole collar</i></li> <li><i>• elevation or RL (Reduced Level – elevation above sea level in metres) of the drill hole collar</i></li> <li><i>• dip and azimuth of the hole</i></li> <li><i>• down hole length and interception depth</i></li> <li><i>• hole length.</i></li> </ul> <p><i>If the exclusion of this information is justified on the basis that the information is not Material and this exclusion does not detract from the understanding of the report, the Competent Person should clearly explain why this is the case.</i></p>	<p><i>See drill hole location plans and figures in main body of the release.</i></p> <p><i>A listing of drill holes and their corresponding coordinates, elevation and depth are listed in Appendix 2.</i></p> <p><i>All drill holes are reported</i></p>

Criteria	Explanation	Comment
Data aggregation methods	<p>In reporting Exploration Results, weighting averaging techniques, maximum and/or minimum grade truncations (eg cutting of high grades) and cut-off grades are usually Material and should be stated.</p> <p>Where aggregate intercepts incorporate short lengths of high-grade results and longer lengths of low-grade results, the procedure used for such aggregation should be stated and some typical examples of such aggregations should be shown in detail.</p> <p>The assumptions used for any reporting of metal equivalent values should be clearly stated.</p>	<p>No grade cutting to assays has been undertaken.</p> <p>Aggregation of samples has been undertaken using simple average calculations for each 1m sample.</p> <p>Assays have been reported as element</p>
Relationship between mineralisation widths and intercept lengths	<p>These relationships are particularly important in the reporting of Exploration Results.</p> <p>If the geometry of the mineralisation with respect to the drill hole angle is known, its nature should be reported.</p> <p>If it is not known and only the down hole lengths are reported, there should be a clear statement to this effect (eg 'down hole length, true width not known').</p>	<p>The W2 project is mostly flat lying exhibiting a gentle dip of mineralisation to the east and 90-degree (vertical) drill holes considered appropriate.</p> <p>Down hole widths are reported</p>
Diagrams	<p>Appropriate maps and sections (with scales) and tabulations of intercepts should be included for any significant discovery being reported These should include, but not be limited to a plan view of drill hole collar locations and appropriate sectional views.</p>	<p>Refer images within the body of this release for further details.</p>
Balanced reporting	<p>Where comprehensive reporting of all Exploration Results is not practicable, representative reporting of both low and high grades and/or widths should be practiced to avoid misleading reporting of Exploration Results.</p>	<p>The exploration results reported here are representative of the mineralisation drill at W2. The holes from which the samples were selected were taken from across the strike length of the deposit to establish grade variability across the known mineralisation.</p>
Other substantive exploration data	<p>Other exploration data, if meaningful and material, should be reported including (but not limited to): geological</p>	<p>At W2 IP surveys have been undertaken and have been found to be useful in identifying high chargeability and low resistivity anomalies associated with manganese mineralisation.</p>

For personal use only

For personal use only

Criteria	Explanation	Comment
	<p><i>observations; geophysical survey results; geochemical survey results; bulk samples – size and method of treatment; metallurgical test results; bulk density, groundwater, geotechnical and rock characteristics; potential deleterious or contaminating substances.</i></p>	
<p><i>Further work</i></p>	<p><i>The nature and scale of planned further work (eg tests for lateral extensions or depth extensions or large-scale step-out drilling).</i></p> <p><i>Diagrams clearly highlighting the areas of possible extensions, including the main geological interpretations and future drilling areas, provided this information is not commercially sensitive.</i></p>	<p><i>DDIP surveys could be used to identify buried stratabound and fault hosted mineralisation prior to any further drilling. The IP surveys could be completed along strike to the north and to the east.</i></p> <p><i>Gravity surveys might also detect deeper buried mineralisation associated with the underlying sedimentary sequences.</i></p>

**APPENDIX 2: SUMMARY DRILL HOLE COLLAR FOR W2 AND KR2**

Hole id	East (WGS84 - Z51)	North (WGS84 - Z51)	RI	EOH	Dip	Azimuth	Deposit
WDRC001	322572	7524001	419	20	-90	360	W2
WDRC002	322602	7523998	415	20	-90	360	W2
WDRC003	322639	7524000	410	70	-90	360	W2
WDRC004	322677	7523999	410	20	-90	360	W2
WDRC005	322717	7524003	412	20	-90	360	W2
WDRC006	322760	7524002	412	20	-90	360	W2
WDRC007	322785	7524001	409	40	-90	360	W2
WDRC008	322557	7523886	422	20	-90	360	W2
WDRC009	322601	7523882	421	20	-90	360	W2
WDRC010	322634	7523880	418	20	-90	360	W2
WDRC011	322681	7523877	414	20	-90	360	W2
<b>WDRC012</b>	<b>322723</b>	<b>7523872</b>	<b>418</b>	<b>20</b>	<b>-90</b>	<b>360</b>	<b>W2</b>
<b>WDRC013</b>	<b>322760</b>	<b>7523884</b>	<b>406</b>	<b>20</b>	<b>-90</b>	<b>360</b>	<b>W2</b>
WDRC014	322759	7523837	409	20	-90	360	W2
WDRC015	322722	7523839	415	12	-90	360	W2
WDRC016	322555	7523920	424	12	-90	360	W2
WDRC017	322596	7523923	427	12	-90	360	W2
WDRC018	322640	7523920	424	12	-90	360	W2
WDRC019	322679	7523918	423	12	-90	360	W2
WDRC020	322717	7523915	416	12	-90	360	W2
WDRC021	322762	7523926	418	20	-90	360	W2
WDRC022	322577	7523962	425	12	-90	360	W2
WDRC023	322595	7523961	424	12	-90	360	W2
WDRC024	322638	7523956	417	12	-90	360	W2
WDRC025	322669	7523958	416	12	-90	360	W2
<b>WDRC026</b>	<b>322725</b>	<b>7523963</b>	<b>410</b>	<b>12</b>	<b>-90</b>	<b>360</b>	<b>W2</b>
<b>WDRC027</b>	<b>322763</b>	<b>7523960</b>	<b>408</b>	<b>20</b>	<b>-90</b>	<b>360</b>	<b>W2</b>
WDRC028	322570	7524014	416	12	-90	360	W2
WDRC029	322599	7524023	415	12	-90	360	W2
WDRC030	322630	7524033	414	12	-90	360	W2
<b>WDRC031</b>	<b>322720</b>	<b>7524056</b>	<b>395</b>	<b>20</b>	<b>-90</b>	<b>360</b>	<b>W2</b>
<b>WDRC032</b>	<b>322753</b>	<b>7524061</b>	<b>402</b>	<b>20</b>	<b>-90</b>	<b>360</b>	<b>W2</b>
WDRC033	322726	7524082	401	20	-90	360	W2
WDRC034	322693	7524077	409	12	-90	360	W2
WDRC035	322661	7524047	413	12	-90	360	W2
KRRC113	281598	7472509	492	30	-90	360	KR2
KRRC114	281505	7472400	499	36	-90	360	KR2
KRRC115	281297	7472296	501	30	-90	360	KR2
KRRC116	281404	7472298	512	36	-90	360	KR2
KRRC117	281501	7472302	512	42	-90	360	KR2

For personal use only



KRRC118	281602	7472301	511	24	-90	360	KR2
KRRC119	281201	7472193	508	24	-90	360	KR2
KRRC120	281395	7472196	510	30	-90	360	KR2
KRRC121	281603	7472198	512	24	-90	360	KR2
KRRC122	281201	7472097	512	18	-90	360	KR2
KRRC123	281302	7472097	510	30	-90	360	KR2
KRRC124	281398	7472098	506	30	-90	360	KR2
KRRC125	281498	7472093	505	30	-90	360	KR2
KRRC126	281600	7472099	516	36	-90	360	KR2
KRRC127	281698	7472101	501	30	-90	360	KR2
KRRC128	281701	7472005	502	30	-90	360	KR2
KRRC129	281505	7471995	510	30	-90	360	KR2
KRRC130	281303	7472007	509	24	-90	360	KR2
KRRC131	281300	7471897	509	18	-90	360	KR2
KRRC132	281401	7471892	512	30	-90	360	KR2
KRRC133	281502	7471891	515	30	-90	360	KR2
KRRC134	281599	7471899	511	36	-90	360	KR2
KRRC135	281704	7471902	514	24	-90	360	KR2
KRRC136	281302	7471790	513	18	-90	360	KR2
KRRC137	281502	7471799	509	30	-90	360	KR2
KRRC138	281711	7471799	507	18	-90	360	KR2
KRRC139	281701	7471701	504	18	-90	360	KR2
KRRC140	281603	7471694	506	18	-90	360	KR2
KRRC141	281508	7471702	507	36	-90	360	KR2
KRRC142	281405	7471696	507	30	-90	360	KR2
KRRC143	281622	7471585	524	40	-90	360	KR2

For personal use only

**APPENDIX 3: Laboratory and pXRF analysis results for selected holes at W2**

HoleID	From	to	Sample ID	Mn %	Fe %	pXRF Mn %	pXRF Fe %
WDRC012	0	1	W2-36	15.1	5.87	13.9	6.61
WDRC012	1	2	W2-37	3.45	2.57	4.2	2.85
WDRC012	2	3	W2-38	2.07	1.48	3.3	1.84
WDRC013	1	2	W2-28	3.05	4.01	3.6	3.88
WDRC013	2	3	W2-29	12.8	4.34	11.1	4.54
WDRC013	3	4	W2-30	34.5	3.35	31.2	4.3
WDRC013	4	5	W2-31	7.81	1.73	8.0	1.96
WDRC013	5	6	W2-32	13.6	2.01	10.4	1.85
WDRC013	6	7	W2-33	35.2	2.35	32.3	3
WDRC013	7	8	W2-34	50.6	1.92	53.3	2.67
WDRC013	8	9	W2-35	24.6	5.01	25.9	6.88
WDRC026	0	1	W2-24	20.4	2.92	22.0	3.89
WDRC026	1	2	W2-25	43.1	1.7	43.7	2.88
WDRC026	2	3	W2-26	31.7	4.38	29.9	5.34
WDRC026	3	4	W2-27	2.52	1.33	3.4	1.53
WDRC027	2	3	W2-16	3.45	6.76	4.1	7.21
WDRC027	3	4	W2-17	4.07	5.5	4.6	5.89
WDRC027	4	5	W2-18	30.8	8.16	30.4	10.35
WDRC027	5	6	W2-19	35.5	5.18	33.3	6.69
WDRC027	6	7	W2-20	16.5	2.5	15.9	3.1
WDRC027	7	8	W2-21	40.5	1.98	40.7	2.77
WDRC027	8	9	W2-22	38.6	4.03	38.8	5.45
WDRC027	9	10	W2-23	3.97	1.73	4.7	2.1
WDRC031	0	1	W2-09	9.49	4.94	9.2	5.35
WDRC031	1	2	W2-10	33.8	2.76	31.4	3.45
WDRC031	2	3	W2-11	14.5	2.8	15.6	3.39
WDRC031	3	4	W2-12	29.8	2.2	30.7	2.82
WDRC031	4	5	W2-13	47	1.09	44.2	1.75
WDRC031	5	6	W2-14	41.1	4.35	38.9	5.26
WDRC031	6	7	W2-15	2.84	1.38	3.8	1.65
WDRC032	2	3	W2-01	3.28	4.29	3.5	4.27
WDRC032	3	4	W2-02	3.73	3.7	4.1	3.73
WDRC032	4	5	W2-03	32.7	2.41	29.0	2.89
WDRC032	5	6	W2-04	13.6	1.45	13.5	1.89
WDRC032	6	7	W2-05	22.4	2.28	22.4	2.73
WDRC032	7	8	W2-06	43.5	1.56	40.2	2.11
WDRC032	8	9	W2-07	53.8	1.04	55.8	1.61
WDRC032	9	10	W2-08	11.7	3.48	9.6	3.42

For personal use only